


Chemistry - Food Chemistry

Biochemistry - Microbiology

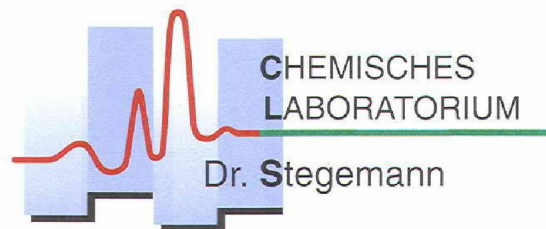

Chemical Laboratory Dr. Stegemann
Leimbrink 2 - D-49124 Georgsmarienhütte

Conica AG

Industriestraße 26
CH-8207 Schaffhausen

From the chamber of commerce publicly appointed
and sworn court-appointed expert for chemistry,
chemistry of waste, physical and chemical
testing of synthetic materials, oils, building materials
and corrosion.

Water-Waste Water-Drinking Water -Technical
Water-Groundwater-Soil-Food-Hygiene-Objects of Daily
Use-Industrial Waste-Advisory Service in Waste Water
Disposal-Material Testing- consulting-
Court Expert's Evidence for Material Damages

2022-01-10

Page 1 of 2

Analysis Report

121120479

Entry of Sample : Package Service at 2021-12-13
Sample : **Muster CONIPUR 2LX + 30x30cm**
Package : wrapped in Aluminium foil and plastic bag
Period of Testing : from 2021-12-16 to 2022-01-06

Parameter	Actual Value	Limit Values	Unit
Method			
Analysis of the original material			
Extractable Organic Halogens	<2,0	100	mg/kg DM
DIN 38414 S-17:2017-01			
Phthalates Sum 10 Compounds	13	--	mg/kg
DIN 18035: 2019-12			
Phthalate Single compound DIBP	4,2	1000	mg/kg
DIN 18035: 2021-08			
Phthalate Single Compound DBP	5,4	1000	mg/kg
DIN 18035: 2021-08			
Phthalate Single Compound DEHP	3,7	1000	mg/kg
DIN 18035: 2021-08			
Phthalate Single Compound BBP	<1	1000	mg/kg
DIN 18035: 2021-08			
Nonylphthalate Mixture	n.b.	--	
GC-MS *			
Decylphthalate Mixture	neg.	--	
GC-MS *			
Chlorinated Paraffins (SCCP)	<80	1500	mg/kg
Toluol Extraction / GC-ECD			
Chlorinated Paraffins (MCCP)	<80	--	mg/kg
Toluol Extraction / GC-ECD			

The results in this report relate only
to the items tested or calibrated.
This report shall not be reproduced
except in full without the written
approval of the testing laboratory

Accredited Laboratory:
Phone +49 5401 8636-0
FAX + 49 5401 8636-36
info@labor-stegemann.de
www.labor-stegemann.de



Parameter	Actual Value	Limit Values	Unit
Method			
24 h eluate according to RAL 943/DIN 18035-6:2021			
DOC	21	50	mg/l
Photometric acc. to Lange			
Lead	<1	25	µg/l
DIN EN ISO 11885:2009-09/ UCL			
Cadmium	<0,3	5	µg/l
DIN EN ISO 11885:20069-09/ UCL			
Chrome	<1	50	µg/l
DIN EN ISO 11885:20069-09/ UCL			
Chromate (VI)	<0,008	0,008	mg/l
DIN 38405 D40 2007-02			
Mercury	<1	1	µg/l
DIN EN ISO 12846 E-12:2012-08			
Zinc	0,03	0,50	mg/l
DIN 38406 E8:2004-10			
Tin	<0,001	0,04	mg/l
DIN EN ISO 11885:20069-09/ UCL			

Assessment

The material meets the requirements of the environmental impact assessment according to DIN V 18035-6:2021-08

D. Stegemann

Dr. Dirk Stegemann
- Chemist / Test Chord -

The results in this report relate only to the items tested or calibrated. This report shall not be reproduced except in full without the written approval of the testing laboratory

Accredited Laboratory:
Phone +49 5401 8636-0
FAX + 49 5401 8636-36
info@labor-stegemann.de
www.labor-stegemann.de



Deutsche
Akkreditierungsstelle
D-PL-14080-01-00